

Constraints in sustainable electrode materials development for solid oxide fuel cell: A brief review

Lukman Ahmed Omeiza^{a,b,**}, Asset Kabyshev^{a,*}, Kenzhebatyr Bekmyrza^{a,*}, Kairat A. Kuterbekov^a, Marzhan Kubenova^a, Zhuldyz A. Zhumadilova^a, Yathavan Subramanian^b, Muhammed Ali^c, Nursultan Aidarbekov^{a,*}, Abul Kalam Azad^{b,*}

^a Faculty of Physics and Technical Sciences, L.N. Gumilyov Eurasian National University, Astana 010008, Kazakhstan

^b Faculty of Integrated Technologies, Universiti Brunei Darussalam, Jalan Tungku Link, Gadong BE1410, Brunei

^c Fuel Cell Institute, Universiti Kebangsaan Malaysia, Bangi 43600, Selangor, Malaysia

ARTICLE INFO

Keywords:

Electrode materials
Solid oxide fuel cell
Sustainability
Polarization resistance
CO₂

ABSTRACT

Solid oxide fuel cells (SOFCs) are efficient electrochemical energy device that converts the chemical energy of fuels directly into electricity. It has a high power and energy density and a sustainable source of energy. The electrode (cathode and anode) materials are essential for the efficient operation of SOFCs. Several electrode materials have been studied in the last two decades, mainly perovskite materials. The investigated materials have resulted in improved electrochemical performance of SOFCs, increased commercial viability, and reduced operational costs. However, the sustainability of most of the material compositions (heteroatoms) used as electrodes in SOFCs has never been investigated. The present study examines the recent progress, challenges, and constraints associated with electrode material development in SOFCs from a sustainable perspective. Heteroatoms majorly employed for doping in electrode materials' long-term availability on the earth's surface was established. The study also provides an overview on the current state of electrode materials development for symmetrical solid oxide fuel cells. This is intended to address the complexities of different materials development for the anode and cathode.

1. Introduction

Overreliance on fossil fuels as the primary source of energy poses a significant challenge to the environment. This form of energy is unsustainable in the long term and has adverse effects on the climate, resulting in the depletion of ozone layers. Among the drawbacks associated with fossil fuels are CO₂ emissions, greenhouse gas effects, the release of nitrogen oxides, and particulates. Energy experts are of the view that there is a need for increased use of sustainable energy-generating technologies [1,2], as it will increase the amount of clean energy available to the global community. Currently, there are several clean energy technologies, including sunlight energy harvesting devices (solar collectors and photovoltaic collectors), biomass, hydrothermal,

wind turbines, and fuel cells [3–5]. Most of these technologies are limited by environmental constraints, such as overcast days, intermittency, and low energy conversion rates. However, fuel cell has proven to have high energy conversion rates (around 60 %), less environmental dependence, and cost-effective compared to other sustainable energy-generating devices. Without the requirement for direct combustion as an intermediate step, fuel cells electrochemically convert chemical energy into electrical energy and heat, resulting in higher conversion efficiency than those of conventional clean energy technologies. The absence of the combustion chamber in fuel cells makes it eco-environmental friendliness [6,7]. Various types of fuel cell technologies exist, including polymer electrolyte membrane fuel cell (PEMFC), solid oxide fuel cell (SOFC), direct methanol fuel cell (DMFC), alkaline

Abbreviations: LNO, lanthanum nickelate; SDC, Samarium doped ceria; LSM, Lanthanum strontium manganite; GDC, Gadolinium-doped ceria; YSZ, Yttria stabilized zirconia; ORR, Oxygen reduction reaction; LSC, Lanthanum strontium cobaltite; LSCM, Lanthanum strontium chromium manganite; SOFC, Solid oxide fuel cell; SSOFC, Symmetrical solid oxide fuel cell.

* Corresponding authors.

** Corresponding author at: Faculty of Physics and Technical Sciences, L.N. Gumilyov Eurasian National University, Astana 010008, Kazakhstan.

E-mail addresses: lukahmed378@gmail.com (L.A. Omeiza), assetenu@gmail.com (A. Kabyshev), kbekmmyrza@yandex.kz (K. Bekmyrza), nursultan02.22.10.92@mail.ru (N. Aidarbekov), abul.azad@ubd.edu.bn (A.K. Azad).

<https://doi.org/10.1016/j.mset.2024.07.001>

Received 1 May 2024; Received in revised form 14 June 2024; Accepted 11 July 2024

Available online 14 July 2024

2589-2991/© 2024 The Authors. Publishing services by Elsevier B.V. on behalf of KeAi Communications Co. Ltd. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

fuel cell (AFC), phosphoric acid fuel cells (PAFC), and molten carbonate fuel cell (MCFC). However, SOFC have shown excellent properties due to its durability and flexibility with fuels, high energy and power densities compared to other electrochemical energy conversion devices.

The three main components of the SOFC are the cathode, electrolyte, and anode. Anode (negative electrode) in fuel cells is responsible for oxidizing hydrogen, releasing electrons and producing protons. The protons then travel via an electrolyte to the cathode (positive electrode), where they combine with oxygen to produce water, releasing more electrons in the process. Electrical current is produced as the electrons flow through an external circuit. Accelerating the oxidation and reduction reactions taking place at the electrodes with electrocatalyst materials such as platinum and other transition metals, ensures the effective conversion of chemical energy to electrical energy [8–10]. However, platinum catalysts are expensive and their electrocatalytic properties tend to decrease after prolonged use in SOFC. This can be attributed to the high operating temperatures of traditional SOFC. Fig. 1 provides an overview of the conventional SOFC and its various components.

The performance and durability of SOFCs is mainly influenced by the selection and optimization of electrode materials. Advancements in electrode materials development have been a major focal point for the past few decades. The present study aims to examine the recent progress in electrode material development for SOFC from a sustainable perspective, while highlighting its limitations. Electrode materials development for symmetrical solid oxide fuel cell were also investigated. Various materials employed in electrode synthesis were analysed, including perovskites, composites, cermet materials, and mixed ionic-electronic conductors. This group of materials was mainly analysed due to their high conductivity, stability at high temperatures, and compatibility with oxygen reduction and fuel oxidation reactions. Although several review studies have been published in the past decade, none was devoted to the sustainability of electrode materials development in SOFC, particularly the long-term availability of heteroatoms. In order to provide an overview of recent advancements in the application of electrode materials in SOFCs, a brief literature review was conducted. To gather relevant literature, three bibliographic databases (ScienceDirect, Web of Science, and Google Scholar) were searched using keywords such as “fuel cell,” “solid oxide fuel cells,” and “electrode materials”. Fig. 2 provides an overview of how the literature was sourced. Similar techniques have been adopted by other researchers in their review studies [11–13].

Most previous related review studies focused on new materials development, optimizations, and future research trends [14–23]. The availability of the heteroatoms used in electrode materials doping, and its sustainability on the long term has never been investigated. The

review study by Bello et al. [24] on proton conducting SOFC (P-SOFC) provide valuable insight on its effectiveness compared to oxygen conducting SOFC (O-SOFC) in terms of none-dilution of fuels at anode, better theoretical efficiency and optimal performance at low working temperature. However, electrode materials sustainability and availability on the long-term were never investigated. Thus, the main goal of the present study is to provide a brief overview of electrode materials development from a sustainable point of view, focusing mainly on the availability of heteroatoms in the periodic table on the long term. The flowchart in Fig. 3 provides an overview on the topics addressed in the present review study.

2. SOFC electrode materials

2.1. Anode materials

The anode of SOFCs is typically made of porous ceramic materials. These ceramic materials can either be nickel-cermet or lanthanum chromite (LaCrO_3) [25,26]. Anodic material must possess high electronic conductivity, robust stability, and effective thermal compatibility with other cell components. It should also possess considerable electrocatalytic efficiency to facilitate oxidation reactions and possess optimal porosity for the effective transport of carrier gases in the high temperature. Several doped perovskite materials have been developed over the past few years as possible anode materials. Nickel anode-based materials are mainly employed in SOFC due its cost-effectiveness and ease of synthesis. To maintain the required porosity and prevent the sintering of nickel particles at high operating temperatures, the anode materials are dispersed with solid electrolyte materials to form cermet [27,28]. This provides compatible thermal expansion coefficients with the solid electrolyte, preventing any issues associated with adhesion during operation. Solid electrolyte plays a critical role as supporting material for anode, which can impact the anode's catalytic properties. $\text{Ce}_{0.9}\text{Sr}_{0.1}\text{Cr}_{0.5}\text{Mn}_{0.5}\text{O}_{3-\delta}$ (CSCMn) was synthesized via the gel combustion method, and investigated as a potential anode for SOFC using $\text{Ce}_{0.8}\text{Sm}_{0.2}\text{O}_{1.9}$ (SDC) electrolyte [29]. The CSCMn demonstrated excellent chemical compatibility with SDC in N_2 environment, but showed structural changes and sulfide formation after exposure to 5 % $\text{H}_2\text{S}-\text{N}_2$ at 800 °C. The effect of sulfide formation on the electrochemical performance of the material needs to be investigated. Further experiments are needed to analyse the changes induced by the new phase.

In recent years, efforts have been centred on investigating electrical conducting oxides as potential alternatives to Ni-based anode materials [30,31]. These oxides have demonstrated good stability under oxidizing and reducing conditions. The use of oxides as anode in SOFC presents an

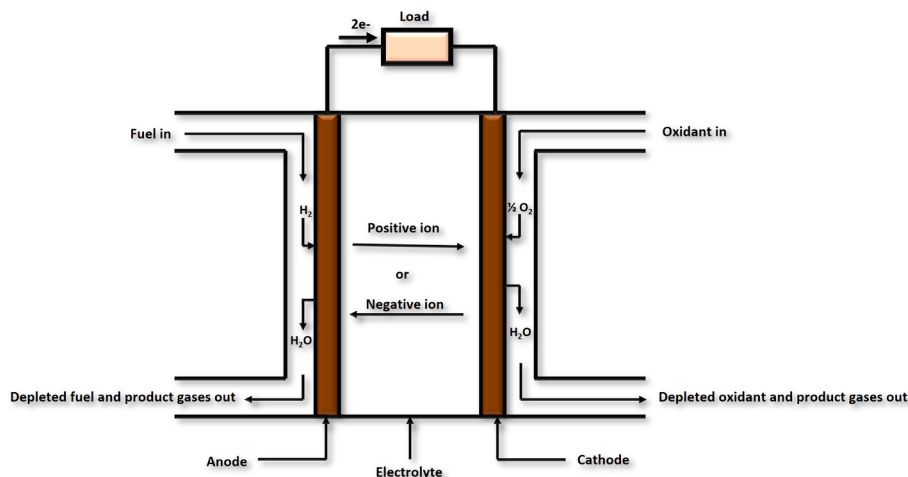


Fig. 1. Schematic diagram of a generalized solid oxide fuel cell.

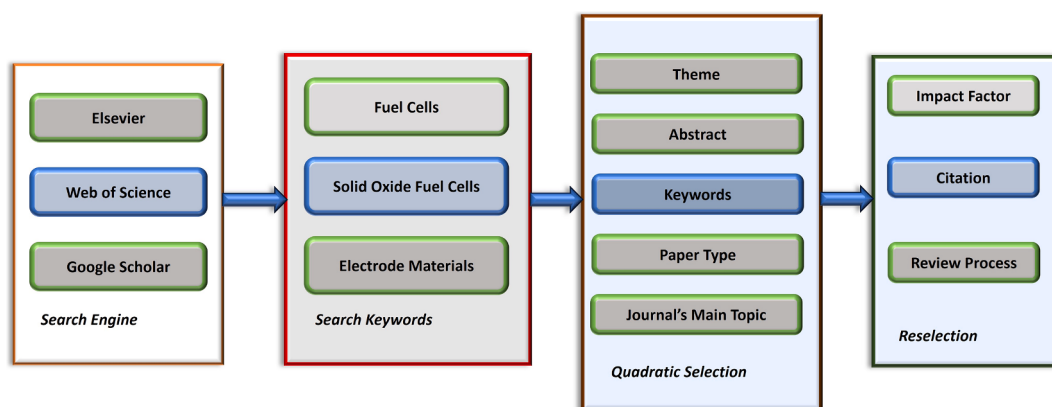


Fig. 2. Methodology adopted in the present study.

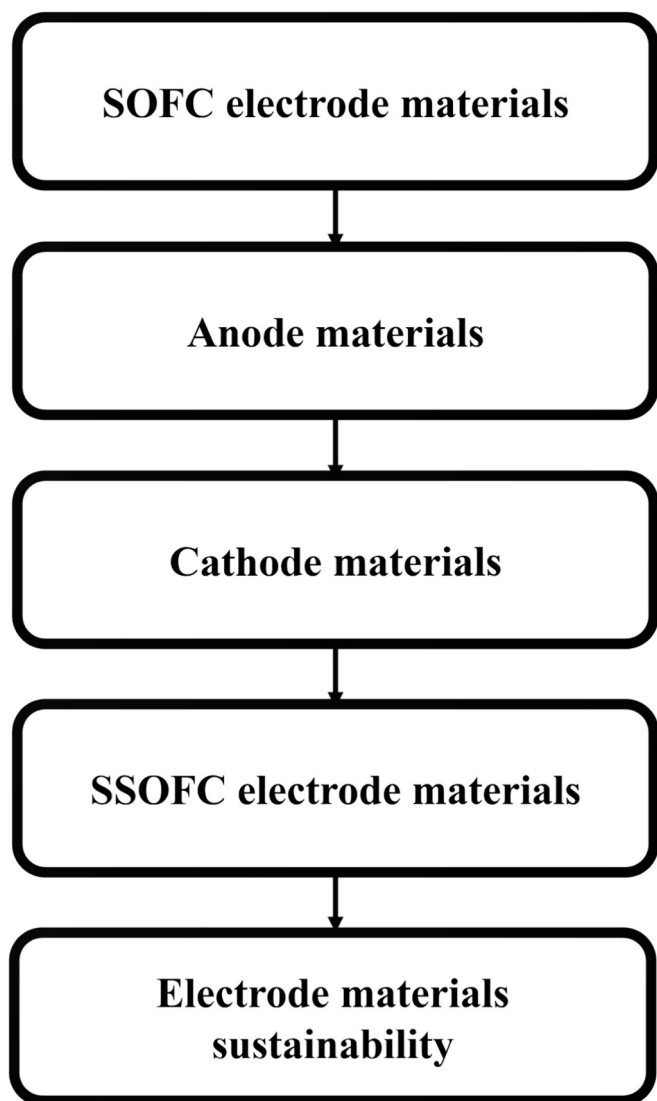


Fig. 3. Overview of the topics addressed in the present study.

exciting solution to the various challenges associated with nickel cermet anodes, including carbon deposition, sulphur poisoning, sintering, and the potential formation of nickel oxide under an oxidizing environment. Oxides showing promise as potential anode materials include lanthanum chromite (LaCrO_3) and strontium titanate (SrTiO_3), both of which have

been extensively investigated along with various doping of A and B sites [32–34]. $\text{La}_{0.7}\text{Sr}_{0.3}\text{Cr}_{0.8}\text{Ti}_{0.2}\text{O}_3$ has been analysed as possible replacement for LaCrO_3 (lanthanum chromite) series [35,36]. While strontium titanate has also been investigated with niobium and lanthanum substitutions, such as $\text{Sr}_{0.6}\text{Ti}_{0.2}\text{Nb}_{0.8}\text{O}_3$ and $\text{La}_{0.4}\text{Sr}_{0.6}\text{TiO}_3$ [37]. Among the new series of perovskite anode materials that were recently synthesised, those belonging to LaCrO_3 demonstrated good anodic properties, low polarization resistance and low thermal expansion coefficient. Furthermore, mixed-conducting oxides such as terbia- and titania-doped YSZ, with yttria-doped ceria, have demonstrated potential to be an excellent anode material since it can significantly reduce overpotential losses at the anode. Fig. 4 illustrates the good polarisation resistance in $\text{La}_{0.75}\text{Sr}_{0.25}\text{Cr}_{0.5}\text{Mn}_{0.5}\text{O}_{3-\delta}$ (LSCM) anode material series with CGO electrolyte. The maximum values of polarisation resistance reported for this group of materials are less than $0.3 \text{ } \Omega/\text{cm}^2$ [38,39]. This facilitates the exchange of charges between the anode-electrolyte interface. Despite the exceptional properties of these materials, pure LSCM demonstrated limited activity in the oxidation of H_2S -free fuels. Nevertheless, it displayed a superior balance between high chemical stability in a sulfur/carbon environment and adequate electrical conductivity compared to other anode materials [40]. Thus, LSCM could be a suitable anode matrix, with its properties further optimized depending on the chosen fuel. The sustainability of this group of materials needs to be investigated, as lanthanum-based materials have been heavily used in materials development for energy conversion devices. Its continued availability in the long term and level of depletion are currently unknown. Hence, a comprehensive study is needed to establish its exact reserve on the earth's surface.

A recent investigation identified alternative anode materials that show significant potential for enabling the direct electrocatalytic oxidation of hydrocarbon fuel through the utilization of electrochemically pumped oxygen ions, thus negating the necessity for any additional co-fed oxidant [42–44]. Some of the new anode materials investigated consist of copper-based materials, with substantial amounts of ceria incorporated in addition to YSZ [45,46]. While other options include the addition of yttria-doped ceria to nickel and YSZ. The practicality of using such anodes for direct hydrocarbon oxidation remains uncertain due to the extremely harsh synthesis conditions required. Their long-term performance is also a major concern, as deactivation caused by carbon deposition will likely occur. The development of these anodes is currently an active field of research. Table 1 summarises previous studies on anode materials used for SOFC applications.

Comparative analysis of Table 1 shows that $\text{La}_{0.43}\text{Ca}_{0.37}\text{Ni}_{0.06}\text{Ti}_{0.94}\text{O}_{3-\delta}$ has the highest power density of $0.94 \text{ W}/\text{cm}^2$ at 900°C . This indicates that low doping with La yielded better power density compared to high doping of composite $\text{La}_{0.75}\text{Sr}_{0.25}\text{Cr}_{0.5}\text{Mn}_{0.5}\text{O}_{3-\delta}$ - $\text{Ce}_{0.8}\text{Gd}_{0.2}\text{O}_{1.9}$ at 800°C . Generally, materials with La composition exhibit favourable electrochemical performance and are often

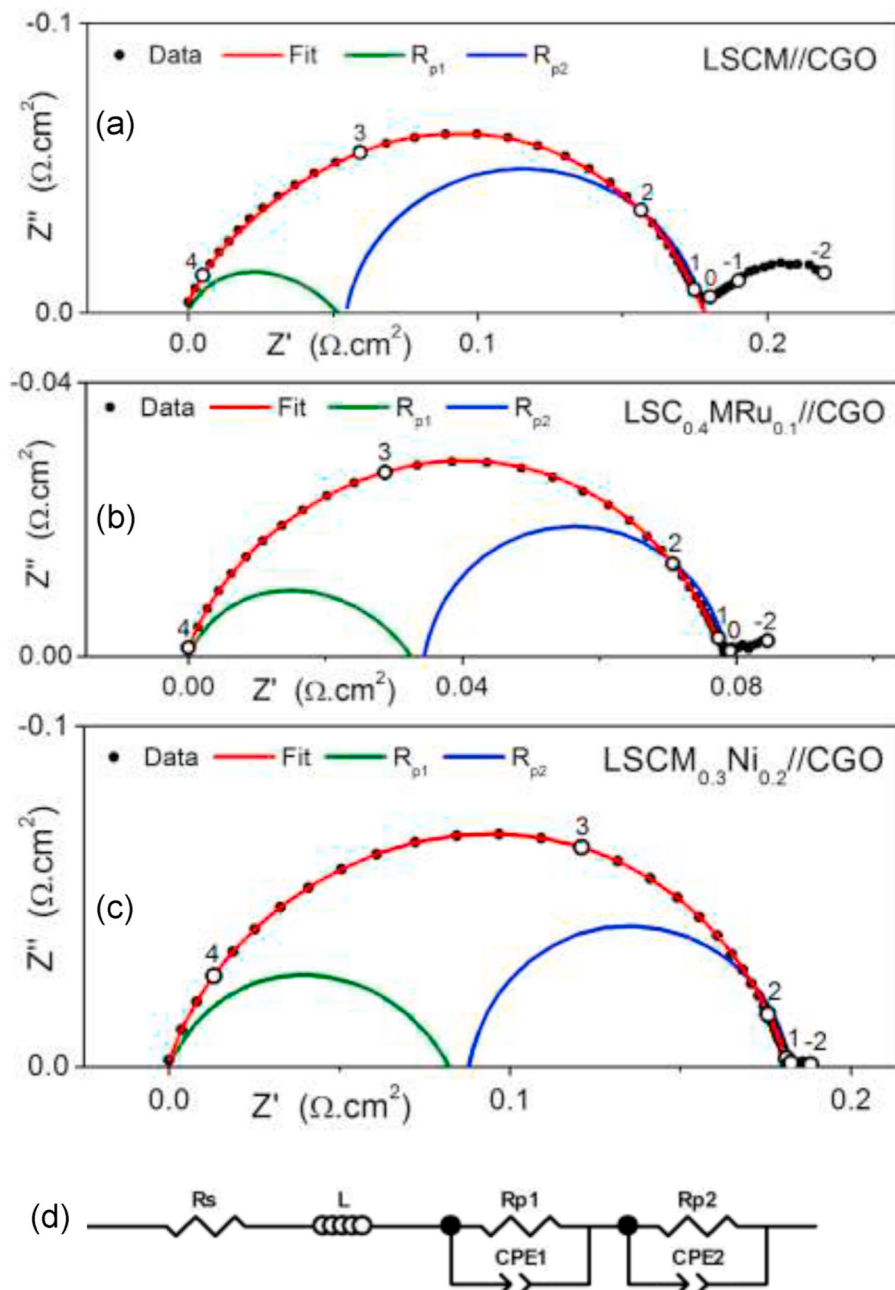


Fig. 4. EIS Nyquist plot obtained at 600 °C under wet Ar/H₂ (5 %) for (a) LSCM-, (b) $\text{LSC}_{0.4}\text{MRu}_{0.1}$ - and (c) $\text{LSCM}_{0.3}\text{Ni}_{0.2}$ -based symmetrical cell, fitted with the equivalent circuit (d) proposed and subtracted from R_s [41].

compatible with commonly used SOFC electrolyte (YSZ/GDC). This compatibility ensures an optimal interfacial contact and minimal interface resistance between the anode and electrolyte, which are crucial for efficient ion transport in SOFCs. However, this group of materials are susceptible to poisoning by certain impurities present in the fuel or atmosphere, such as sulfur compounds. This poisoning can lead to degradation of the anode performance over time and necessitate frequent cleaning or regeneration steps to maintain optimal operation.

2.2. Cathode materials

The cathode materials used in solid oxide fuel cell should have excellent thermal compatibility with electrolyte to avoid delamination during high operating temperatures. It should possess high electronic conductivity, good ionic conductivity and have a porous structure

[63–66]. The cathode plays an important role in SOFC performance, as it is responsible for facilitating the oxygen reduction reaction. To achieve these goals, cathode materials must exhibit low polarization resistance, and good stability. Some of the most used cathode materials in SOFCs include lanthanum strontium manganite (LSM), lanthanum strontium cobaltite (LSC), and lanthanum nickelate (LNO) [67–69]. Other materials such as samarium-doped ceria (SDC) and gadolinium-doped ceria (GDC) can also be used as cathode materials in SOFCs in certain conditions.

In SOFCs, it is a common practice to use cathode with two layers [70]. The initial layer comprises mixed LSM and yttria-stabilized zirconia, which are similar to NiO/YSZ cermet used as anode. This methodology improves the thermal matching between the cathode and zirconia electrolytes, resulting in increased porosity and enhanced resistance to sintering, while preserving the electronic conductivity

Table 1

Various Anode materials investigated for SOFC applications.

Compositions	Temperature (°C)	Maximum power density (W/cm ²)	Ref.
PrBaMn _{1.8} Co _{0.2} O ₅ (PBMCo)	900	0.12	[47]
Fe-Co/PrBa _{0.8} Sr _{0.2} Mn ₂ O ₅	800	0.68	[48]
(LaSr) _{0.9} Fe _{0.9} Cu _{0.1} O ₄ (LSFCu)	800	0.40	[49]
Ce _{0.2} Sr _{0.8} Fe _{0.95} Ni _{0.05} O ₃	800	0.58	[50]
SV _{0.5} Mo _{0.5} Ni _{0.1} O _{4-δ}	800	0.22	[51]
Sm _{0.5} Ba _{0.5} MnO _{3-δ}	800	0.30	[52]
Ag-(La _{0.60} Sr _{0.40}) _{0.95} Co _{0.20} Fe _{0.80} O _{3-x}	800	0.07	[53]
Ni-Ce _{0.6} Mn _{0.3} Fe _{0.1} O ₂	750	0.49	[54]
(PrBa) _{0.95} Fe _{1.4} Cu _{0.4} Nb _{0.2} O _{5+δ}	750	0.27	[55]
CuO-ZnO-SDC	700	0.13	[56]
La _{0.75} Sr _{0.25} Co _{0.5} Mn _{0.5} O _{3-δ}	800	0.36	[40]
Ca ₂ Fe ₂ O ₅ -Ca ₂ Co ₂ O ₅	800	0.16	[57]
Ba ₂ Fe _{1.5} Mo _{0.5} O _{6-δ}	800	0.908	[58]
SmBa _{0.5} Sr _{0.5} Co _{1.5} Fe _{0.5} O _{5+δ}	825	0.032	[59]
La _{0.43} Ca _{0.37} Ni _{0.06} Ti _{0.94} O _{3-δ}	900	0.94	[60]
La _{0.75} Sr _{0.25} Cr _{0.5} Mn _{0.5} O _{3-δ}	800	0.221	[61]
Ce _{0.8} Gd _{0.2} O _{1.9}			
SrMo _{0.8} Al _{0.2} O _{3-δ}	850	0.633	[62]

[71]. The second layer known as the current collection layer is entirely composed of LSM. Integrating platinum into LSM cathodes has demonstrated efficacy in improving cell performance through the reduction of electrical resistance at the interface between the cathode and the current collector [72–74]. However, the high cost of platinum should be taken into account when utilizing this technique.

Fig. 5 illustrates the thermogravimetry differential thermal analysis (TG-DTA) of an LSM group of perovskites. The TG-DTA profile shows a weight loss at approximately 401 °C, which can be attributed to the evaporation of moisture from the sample and the formation of oxygen vacancies. LSM has some limitations in terms of its electrochemical compatibility with zirconia electrolyte, which usually limits sintering temperatures to below 1300 °C. At temperatures exceeding 1300 °C, manganese has been observed to undergo diffusion into the zirconia electrolyte, resulting in adverse effects on both the cathode and electrolyte components [75]. Despite the high operating temperatures of SOFCs, the extent of manganese diffusion remains minimal, and extensive long-term studies demonstrate no deterioration in the cathode

resulting from the interplay between LSM and the zirconia electrolyte [68,76]. Several investigations have demonstrated that up to a temperature of 1200 °C, there is no evident reaction between LSM and zirconia. However, at temperatures exceeding 1200 °C, the formation of La₂Zr₂O₇ and SrZrO₃ occurs, particularly with increased levels of strontium [77]. The electrical conductivity of La₂Zr₂O₇ is over 100 times less than that of zirconia. Fig. 6 shows the morphology analysis of highly porous LSM series of cathode materials.

Doped lanthanum cobaltite (LaCoO₃) has been extensively explored as a cathode material in SOFCs owing to its inherent p-type conductivity and the notable oxygen deficit it exhibits at elevated temperatures [79]. The substitution of divalent cation, especially strontium on the lanthanum site can increase its conductivity, and further performance enhancements can be achieved by replacing iron on the cobalt site [80]. LaCoO₃ exhibits superior electrical conductivity compared to LaMnO₃ under similar conditions [81]. However, its use as cathode material in zirconia-based SOFCs is generally limited due to its reactivity towards zirconia and its ability to undergo reduction at high temperatures. Moreover, LaCoO₃ exhibits a substantially larger thermal expansion coefficient than LaMnO₃, which already surpasses that of yttria-stabilized zirconia [82]. To address these issues, researchers have attempted to enhance the linear thermal elongation of LaCoO₃ to better match that of YSZ electrolyte by mixing LaCoO₃ with LaMnO₃ [83,84]. While primary findings on composite LaCoO₃-LaMnO₃ is interesting, its low polarization resistance at intermediate-temperature requires further optimization.

LSCF has a higher electrical conductivity compared to LSM, which makes it the preferred cathode material for IT-SOFC that uses gadolinia-doped ceria or lanthanum gallate electrolytes [85]. The performance of LSM cathodes is inadequate at low operating temperatures, and significantly restricts the overall SOFCs performance. Currently, there is a considerable emphasis on developing cathode materials that exhibit superior performance at low temperatures (<500 °C). The use of composite cathodes has demonstrated some potential in achieving this goal. Researchers continue to investigate new cathode materials that can improve SOFC performance, such materials must have higher ORR and good thermal coefficient at high temperature. Advancements in cathode materials could lead to more efficient, cost-effective SOFC with broader applications in energy generation. Table 2 gives an overview of previously investigated cathode materials for SOFC application.

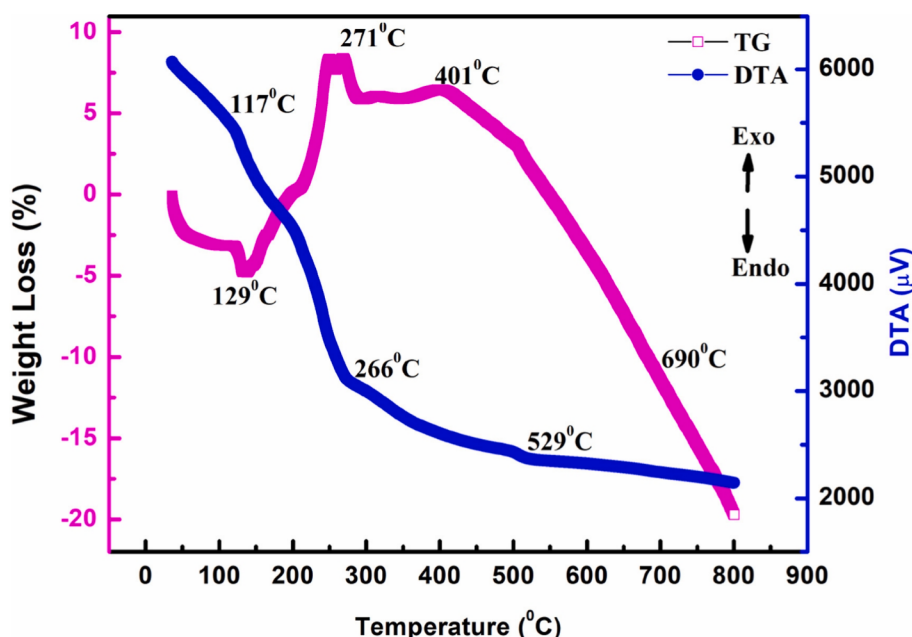


Fig. 5. TG-DTA profile of LSMN7382 dry gel at a temperature of 40–800 °C [78].

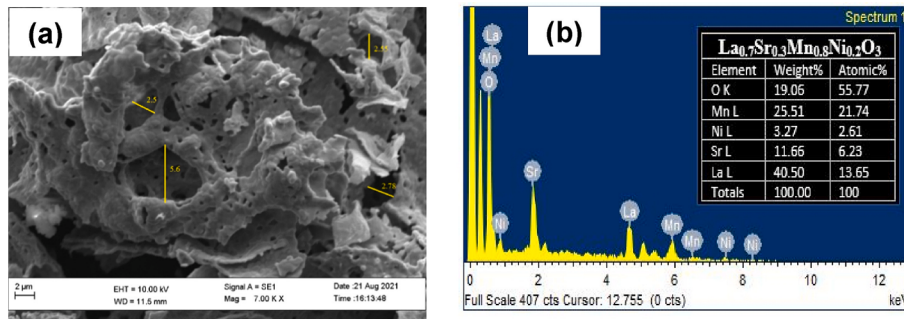


Fig. 6. (a) Scanning electron microscope (SEM) of LSMN7382 nanopowder and (b) corresponding elemental analysis (EDAX) [78].

Table 2

Previous studies on cathode materials for SOFCs application.

Compositions	Temperature (°C)	Polarization resistance (Ohm/cm ²)	Ref
Nd _{0.5} Ba _{0.5} Zr _{0.5} Fe _{0.2} O _{3+δ}	800	0.206	[86]
Ba _{0.5} Sr _{0.5} Co _{0.8} Fe _{0.2} O _{3-δ}	600	0.45	[87]
Sm _{0.2} Ce _{0.8} O _{1.9}			
CuBi ₂ O ₄	700	0.58	[88]
PrBaFe _{1.9} Mo _{0.1} O _{5+δ}	800	0.092	[89]
NdBaCo _{1.5} Cu _{0.5} O _{5+δ}	700	0.67	[90]
BaZr _{0.125} Y _{0.125} Fe _{0.75} O ₃	600	0.18	[91]
40CuFe ₂ O ₄ -60GDC	800	1.17	[92]
PrBaCo ₂ O _{5+δ}	800	0.181	[93]
La _{0.7} Sr _{0.3} Co _{0.25} Fe _{0.25} Ni _{0.25} Mn _{0.25} O _{3-δ}	600	5.24	[94]
PrBa _{0.8} Ca _{0.2} Co ₂ O _{5+δ}	700	0.166	[95]
La _{0.8} Sr _{0.2} Co _{0.2} Fe _{0.8} O _{3-δ}	750	0.16	[96]
δ@Gd _{0.2} Ce _{0.8} O _{1.9}			
Sr ₂ Fe _{1.5} Sc _{0.5} O _{6-δ}	700	0.043	[97]
Sm _{0.5} Sr _{0.5} CoO ₃	700	0.5	[98]
Sr ₂ Fe _{1.5} Mo _{0.4} In _{0.1} O _{6-δ}	800	0.046	[99]
Ba _{0.5} Sr _{0.5} (Co _{0.8} Fe _{0.2}) _{0.96} Zn _{0.04} O _{3-δ}	600	0.23	[100]
Nd _{1.5} Ba _{1.5} CoFeMnO _{9-δ}	700	1.1273	[101]
La _{0.8} Ba _{0.1} Bi _{0.1} FeO ₃	550	0.33	[102]
Ba(Co _{0.4} Fe _{0.4} Zr _{0.1} Y _{0.1}) _{0.95} Ni _{0.05} O _{3-δ}	550	0.607	[103]

In Table 2, Sr₂Fe_{1.5}Sc_{0.5}O_{6-δ} has a polarization resistance of 0.043 Ohm/cm² at 700 °C, followed by cobalt-containing materials, with Ba_{0.5}Sr_{0.5}(Co_{0.8}Fe_{0.2})_{0.96}Zn_{0.04}O_{3-δ} having a polarization resistance of 0.23 Ohm/cm² at 600 °C. A critical overview of Table 2 also showed that cobalt-containing cathode materials has better R_p at low temperatures compared to cobalt-free cathode materials. Cobalt-containing oxides possess a balanced combination of electronic and ionic conductivity, which is crucial for efficient charge transport in SOFC cathodes. This balanced conductivity enables rapid oxygen ion diffusion through the cathode material, facilitating oxygen reduction and minimizing polarization losses. However, cobalt-containing perovskite cathodes may react with impurities present in the fuel or air streams, leading to the formation of secondary phases or surface contaminants. These reactions can alter the cathode's surface chemistry, decrease catalytic activity, and increase polarization resistance, ultimately compromising cell performance and durability. High polarization resistance in SOFC electrode materials reduces cell efficiency, and causes voltage loss, lower power output, incomplete fuel utilization, and material degradation. Mitigation strategies include developing advanced materials, doping, optimizing microstructures, and adjusting operating conditions. Furthermore, cobalt is relatively expensive and sensitive material, with concerns about its supply chain sustainability and environmental impacts. High cost of cobalt can significantly affect the overall cost of SOFCs and limit their widespread commercialization, prompting study on cobalt-free cathode materials.

2.3. Symmetrical solid oxide fuel cell electrode materials

Symmetrical solid oxide fuel cell (SSOFC) offers enhanced thermo-mechanical compatibility between the electrolyte and electrode, cost-effective fabrication, and increased resistance to coking and sulfur poisoning. Initially restricted to electrode materials with stable phase structures in both reducing and oxidizing environments. However, ongoing investigations are exploring novel electrode materials that can undergo beneficial phase transitions or reductions in reducing atmospheres. Meng et al. [104] developed SOFC with tri-layer porous/dense/porous La_{0.9}Sr_{0.1}Ga_{0.8}Mg_{0.2}O_{3-δ} (LSGM) structures and nanoscale SrFe_{0.75}Mo_{0.25}O_{3-δ} (SFMO) catalysts. They observed exceptionally high-power density of 0.97 W/cm² at 800 °C with hydrogen fuel. Impedance measurements showed higher polarization resistances in hydrogen compared to air (0.22 vs 0.04 Ω/cm² at 800 °C). The adsorption of hydrogen on SFMO catalysts and charge transfer at SFMO/LSGM interfaces was identified as rate-limiting steps for hydrogen oxidation at high and low temperatures. Additionally, the composites achieved excellent carbon resistance in iso-octane fuels, reaching a power density of 0.39 W/cm² at 800 °C. Although the results are remarkable, the polarization resistance of 0.22 Ωcm² at 800 °C in a hydrogen environment is too high for effective oxidation of fuel. Gao et al. [105] infiltrated Pr₂NiO₄ (PNO) with SDC to develop a bi-electrode for symmetrical SOFC. In-situ exsolution of Ni nanoparticles on PNO after H₂ reduction increased hydrogen oxidation at the anode. SDC infiltration improved ORR performance at the cathode. The symmetrical cell achieved a maximum power density of 375 mW/cm² at 800 °C with H₂ and air. PNO-40SDC/SDC/PNO-40SDC cells demonstrated no degradation after 168 h at 750 °C and demonstrated stability during H₂/air cycling, suggesting PNO as a promising electro-catalyst for SOFC. However, nickel-based materials faced significant challenges of carbon deposition, leading to a decline in cell performance.

The doping of Ca on the A-site significantly enhances the catalytic efficiency of anodic-cathodic reactions, and improves CO₂ tolerance [106]. Ca-doped Pr_{0.5}Ba_{0.5}FeO₃ (Ca-PBF) electrode exhibits excellent redox resistance, electrochemical activity, and durability. At 700 °C, the polarization resistance was reduced for both cathode and anode, compared to PBF (without Ca-doping). The optimal power density reached 480 mW/cm² with H₂ fuel, indicating Ca-PBF as a suitable electrode material for symmetrical solid oxide fuel cell due to its excellent stability and catalytic activity. In Fig. 7, the electrochemical impedance spectra of PBF/Ca-PBF measured in wet H₂ (3 % H₂) is shown. Zhang et al. [107] investigated the doping effect of Ni, Cu, and Co on the B-site of Sr₂FeNi_{0.2}Cu_{0.2}Co_{0.1}Mo_{0.5}O₆ (SFNCCM). The materials possess good structural stability, excellent thermal compatibility with GDC, and a maximum electrical conductivity of 21.7 S/cm at 800 °C. The average TEC for SFNCCM was estimated to be 18.3 × 10⁻⁶ K⁻¹ at 30–1000 °C. SFNCCM has an area specific resistance of 0.046 Ω cm² at 800 °C, with an optimal power density of 610 mW/cm². However, at high operating temperatures, new phases were formed with increased oxygen vacancies affecting material stability, suggesting

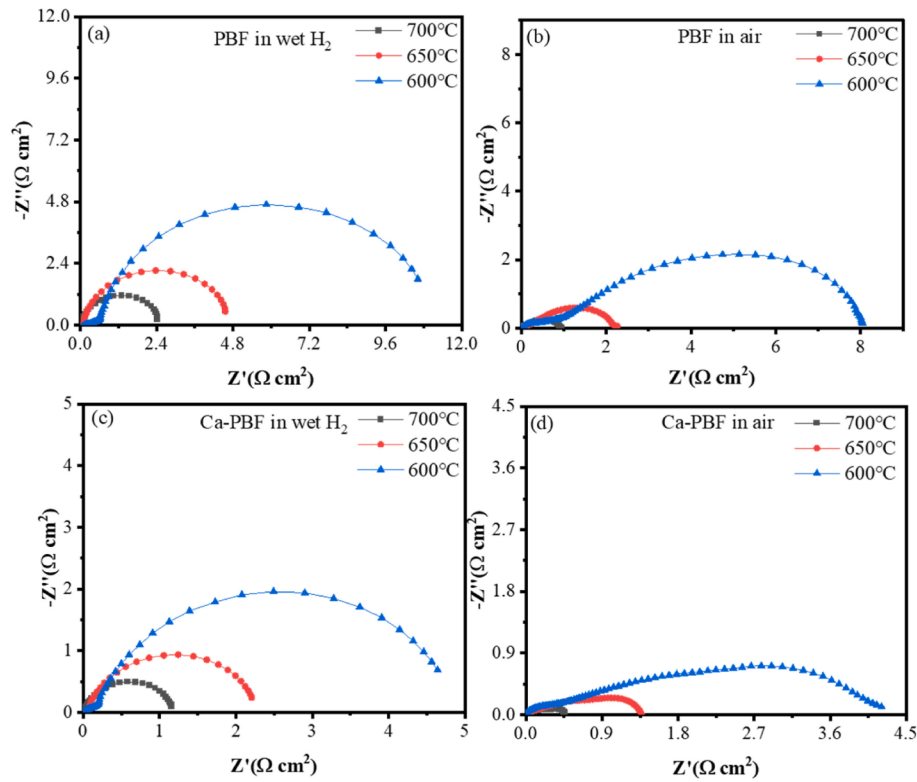


Fig. 7. Electrochemical impedance profile of PBF and Ca-PBF measured in wet H₂ (a, c) and air (b, d) [106].

potential improvement by doping with high-valent or high-bond energy metals. Thus, further studies are needed to improve the stability of this material at high temperatures. Sr and Ge-doped $\text{PrBa}_{0.5}\text{Sr}_{0.5}\text{Fe}_{1.9}\text{Ge}_{0.1}\text{O}_{5+\delta}$ (PBSFG) shows promise compared to $\text{PrBaFe}_2\text{O}_{5+\delta}$ (PBF) as electrode material in SSOFC and CO₂ electrolysis [108]. In SSOFC mode, a stable 1.05 W/cm² power density was achieved at 800 °C. For CO₂ electrolysis, stable mode was attained at 850 °C and 1.5 V. PBSFG shows a high current density of 825 mA/cm² compared to 370 mA/cm² for PBF. The DRT, Tafel slope, XPS, and ECR tests demonstrated improved catalytic activity and improved electrochemical reactions. The high cell performance is attributed to improved oxygen-ion-vacancy concentration and charge-transfer rate, particularly in fuel electrode reactions like CO₂ adsorption and dissociation, suggesting Sr and Ge-doped PBF as a favourable candidate for electrodes in SSOFCs. Table 3 summarises recent findings in symmetrical solid oxide fuel electrode materials development.

Based on the data presented in Table 3, $\text{Sr}_{0.9}\text{Fe}_{0.8}\text{Sc}_{0.1}\text{Co}_{0.1}\text{O}_{3-\delta}$ exhibits the lowest polarization resistance of 0.117 Ohm/cm² at 850 °C, suggesting its potential as electrode material in SSOFC. $\text{Pt@C-Ni}_{0.8}\text{Co}_{0.15}\text{Al}_{0.05}\text{LiO}_{2-\delta}$, operating at a lower temperature of 550 °C, exhibits a higher polarization resistance of 0.24 Ohm/cm², despite the high polarization resistance this material could still be viable for SSOFC electrode if composite $\text{YSZ-Pt@C-Ni}_{0.8}\text{Co}_{0.15}\text{Al}_{0.05}\text{LiO}_{2-\delta}$ /GDC/ $\text{Pt@C-Ni}_{0.8}\text{Co}_{0.15}\text{Al}_{0.05}\text{LiO}_{2-\delta}$ are used. Generally, low

polarization resistance in electrode materials is desirable for SOFC applications. It enhances performance and efficiency by minimizing voltage losses, improving power output, ensuring better fuel utilization, and reducing heat generation and material degradation. The study on symmetrical solid oxide fuel cell is still an active area of research, and more investigations are needed to gain full insight into electrode materials that can provide excellent electrochemical performance as anode and cathode.

2.4. Sustainable electrode development in solid oxide fuel cell

Heteroatoms play a crucial role in improving ionic conductivity, catalytic activity, and overall performance of SOFC. However, their environmental impact and the search for alternative materials are important considerations in the advancement of SOFC technology. Some of the commonly used heteroatoms include nickel, cobalt, lanthanum, yttrium, and cerium, each with associated environmental challenges in extraction and processing. Sustainable strategies involve exploring alternative materials like copper, iron, and bismuth oxide, improving recycling processes, and adopting green synthesis methods. Sustainable electrode materials development for SOFCs involves enhancing performance while reducing costs and environmental impact. The use of novel nanostructured materials, such as perovskites and ceria-based composites, to improve electrochemical activity and stability has endangered some groups of elements in the periodic table. Some elements are rarely used due to issues such as limited availability, toxicity, and challenges in waste management [115,116]. Notably, elements like cobalt (Co) and nickel (Ni), despite their favourable electrochemical properties, present challenges such as scarcity, environmental impact from mining, and difficulties in end-of-life disposal. Nevertheless, recent studies have focused on the development of cobalt-free cathode materials and nickel-free anode materials. Fig. 7 provides an overview on the sustainability profiles of the elements used in electrode materials compositions for SOFCs. The elements not coloured do not have a verified sustainability profile. Current knowledge on their exact reserve is limited, thus urgent

Table 3
Symmetrical solid oxide fuel cell electrode materials.

Material compositions	Temperature (°C)	Polarization resistance (Ohm/cm ²)	Ref.
$\text{Sr}_{0.9}\text{Fe}_{0.8}\text{Sc}_{0.1}\text{Co}_{0.1}\text{O}_{3-\delta}$	850	0.117	[109]
$\text{Pt@C-Ni}_{0.8}\text{Co}_{0.15}\text{Al}_{0.05}\text{LiO}_{2-\delta}$	550	0.24	[110]
$\text{La}_{0.6}\text{Ba}_{0.4}\text{Ni}_{0.2}\text{Fe}_{0.7}\text{Ti}_{0.1}\text{O}_{3-\delta}$	800	0.153	[111]
$\text{Nd}_{0.9}\text{Ce}_{0.1}\text{BaCoFeO}_{5+\delta}$	700	0.078	[112]
$\text{Gd}_2\text{SrCo}_{0.8}\text{Fe}_{1.2}\text{O}_{7-\delta}$	800	0.106	[113]
$\text{Sr}_2\text{Fe}_{1.5}\text{Mo}_{0.5}\text{O}_{6-\delta}$	700	0.62	[114]

studies are needed to explore and understand their estimated remaining deposit. Gold (Au) is highlighted in red in the sustainability ranking, indicating limited availability and emphasising the need for its cautious utilization. Based on verified known reserves, Au has 5–20 years before its known reserves get depleted. However, Au is hardly used in electrode material preparation in SOFC but is mainly employed as current collectors in electrochemical analysis due to its high melting point compared to silver wires.

Several initiatives have been taken to recuperate and recycle metals used in SOFC electrode materials. However, the development of efficient recycling systems remains challenging. The intricate process of separating and recycling mixed-metal electrodes, which often include a variety of elements, presents technical obstacles. Although some metal recovery processes have proven successful, broader implementation is hindered by the complexity of the recovery technique and high cost. There is a growing inclination towards utilizing elements characterized as “green” in Fig. 8 due to their favourable environmental properties, sustainability, and abundant availability. Elements such as manganese (Mn), cobalt (Co), and strontium (Sr) emerge as alternatives to the green elements owing to their minimal toxicity and potential for effective recycling [118]. It is imperative to recognize that achieving complete sustainability in electrode materials development for SOFC may require performance trade-offs. The harmonization of electrochemical efficiency with sustainability criteria remains a persistent challenge in the field of energy materials development. Nonetheless, advancements in green chemistry principles and sustainable practices continue to drive innovation towards more eco-friendliness SOFC electrode materials development.

3. Future research direction on sustainable electrode materials development for SOFC

The high energy conversion rate of SOFC (around 60 %) makes it one of the most effective clean energy technologies. Sustainable electrodes are not only crucial for the long-term survival of SOFC, but also aid in attaining the world objective of a near net-zero emissions by 2050 [119,120]. Hence future research directions must focus on the following:

- Nanostructured composite electrodes have shown excellent electrochemical performance in air and H₂ environments. Hence this set of electrode materials should be prioritised for further investigations in symmetrical SOFC configuration.
- New catalyst materials and integration techniques should be utilized to enhance the mechanism of oxygen reduction and fuel oxidation reactions. The expensive nature of Pt, Co and Ni, means that other novel materials must be investigated.
- Ba, Sr, and Ca have mainly been used as dopants to enhance the thermal stability of electrodes with YSZ and GDC electrolytes. However, the use of Sc as a dopant in Sr_{0.9}Fe_{0.8}Sc_{0.1}Co_{0.1}O_{3–δ} as reported in this study aids in mitigating the thermal degradation of electrodes at high temperature. Future studies need to focus on the use of Sc as a dopant with other series of perovskite materials.
- Developing cost-effective and abundant materials without compromising performance needs to be studied.
- More investigation is needed to understand the exact mechanism for electrode–electrolyte interface optimization for ion and electron transport, reducing polarization losses and improving overall cell efficiency.
- Several investigations have relied on the use of metal oxides as electrode materials, thereby endangering some vital elements in the periodic table. Future studies must be carried out on the possibility of using agricultural waste, and other sustainable means of electrode materials development. However, there specific chemical composition must be investigated, as some of the agricultural waste contains some of the endangered elements in the periodic table.
- Based on the sustainability profile, elements in green should be favoured for future investigations on SOFC electrode materials development. However, highlighted in green colour also include expensive and rare metals like Sc and some lanthanoids, toxic Cr, but doesn't include Fe, hence performance trade-off must be looked into critically over long-term availability in the selection of some specific heteroatoms.
- It is necessary to develop and acceptable methods to determine what are the specific criteria for sustainable electrodes in SOFC. Several gaps remain, and complete knowledge on SOFC sustainable electrodes are limited.

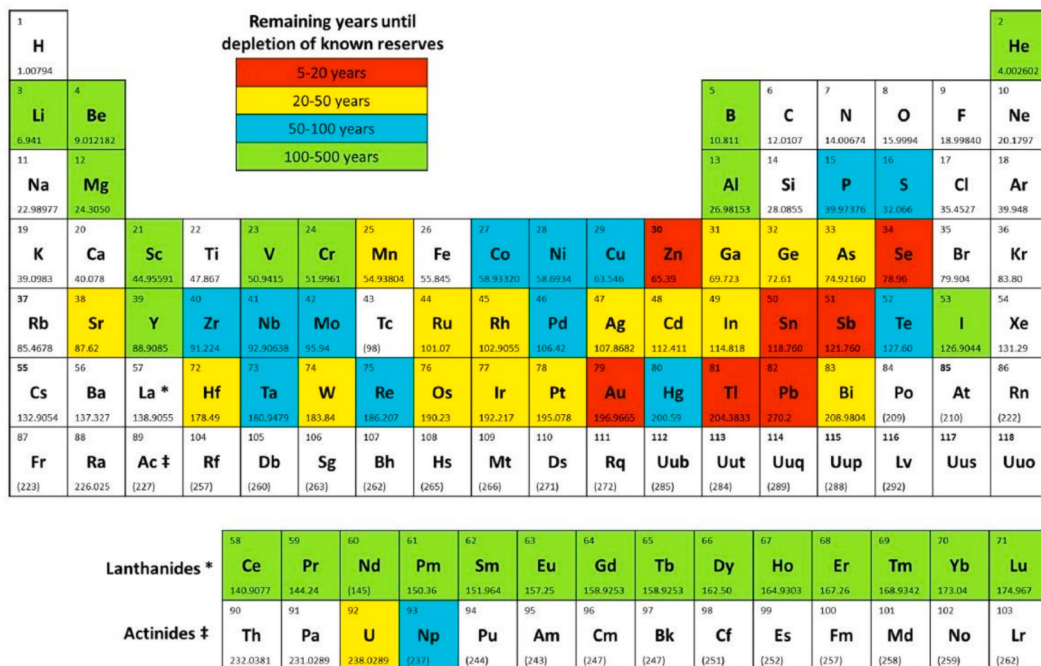


Fig. 8. Sustainable profile of elements in the periodic table [117].

4. Conclusions

Sustainable electrode materials are crucial for enhancing the efficiency, durability, and commercial viability of solid oxide fuel cell. This mini review highlights several key constraints and challenges faced in the development of sustainable electrode materials for SOFCs, paying close attention to the availability of heteroatoms in the long term. The high operating temperatures of SOFCs present a fundamental constraint, limiting the selection of suitable electrode materials to those with excellent thermal stability and conductivity. This has resulted in a continuous search for new materials that can maintain good electrochemical performance and structural integrity under high operating temperatures. The requirement for high electrochemical activity and catalytic efficiency further complicates the search for ideal electrode materials. Several promising materials exhibit insufficient electrochemical performance or suffer from poor chemical stability, hindering their practical application. Strategies to enhance the intrinsic activity and stability of electrode materials, such as nanostructuring, doping, and surface modification, have been investigated but often come with their own set of challenges and limitations. The most efficient electrode material compositions, such as rare earth elements and precious metals are expensive. Furthermore, the environmental impact associated with the extraction, processing, and disposal of these materials raises concerns about the overall sustainability of SOFC technology. The long-term sustainability of heteroatoms, as illustrated in Fig. 7, is also of great concern. Despite these challenges, significant progress has been made in recent years towards the development of sustainable electrode materials for SOFCs. Future studies must investigate the possibility of developing green electrodes, where sustainable materials are given priority.

Funding

This study was supported by the grant with reference number AP 15473333, provided by the Ministry of Science and Higher Education of Kazakhstan.

CRediT authorship contribution statement

Lukman Ahmed Omeiza: Writing – review & editing, Writing – original draft, Visualization, Validation, Methodology, Investigation, Formal analysis, Data curation, Conceptualization. **Asset Kabyshev:** Visualization, Funding acquisition, Conceptualization. **Kenzhebatyr Bekmyrza:** Resources, Investigation, Funding acquisition, Formal analysis. **Kairat A. Kuterbekov:** Visualization, Supervision, Resources, Funding acquisition, Formal analysis, Data curation, Conceptualization. **Marzhan Kubenova:** Visualization, Validation, Project administration, Funding acquisition, Formal analysis, Data curation. **Zhuldiz A. Zhumadilova:** Validation, Methodology, Funding acquisition, Data curation. **Yathavan Subramanian:** Visualization, Validation, Investigation, Funding acquisition, Data curation. **Muhammed Ali:** Writing – review & editing, Validation, Supervision, Formal analysis, Conceptualization. **Nursultan Aidarbekov:** Supervision, Validation, Writing – review & editing. **Abul Kalam Azad:** Writing – original draft, Visualization, Validation, Supervision, Conceptualization.

Declaration of competing interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

References

- [1] A.N. Zainon, M.R. Somalu, A.M. Kamarul Bahrain, A. Muchtar, N.A. Baharuddin, et al., Challenges in using perovskite-based anode materials for solid oxide fuel cells with various fuels: a review, *Int. J. Hydrogen Energy* 48 (2023) 20441–20464, <https://doi.org/10.1016/j.ijhydene.2022.12.192>.
- [2] S.A. Muhammed Ali, M. Anwar, L.S. Mahmud, N.S. Kalib, A. Muchtar, M. R. Somalu, Influence of current collecting and functional layer thickness on the performance stability of $\text{La}_{0.6}\text{Sr}_{0.4}\text{Co}_{0.2}\text{Fe}_{0.8}\text{O}_{3-\delta}\text{-Ce}_{0.8}\text{Sm}_{0.2}\text{O}_{1.9}$ composite cathode, *J. Solid State Electrochem.* 23 (2019) 1155–1164, <https://doi.org/10.1007/s10008-019-04208-6>.
- [3] A.M. Norouzi, M. Siavashi, O.M. Khaliji, Efficiency enhancement of the parabolic trough solar collector using the rotating absorber tube and nanoparticles, *Renew. Energy* 145 (2020) 569–584, <https://doi.org/10.1016/j.renene.2019.06.027>.
- [4] Y. Lai, Z. Wang, D. Cui, F. Han, Y. Ji, W. Cai, Thermal impact performance study for the thermal management of ammonia-fueled single tubular solid oxide fuel cell, *Int. J. Hydrogen Energy* 48 (2023) 2351–2367, <https://doi.org/10.1016/j.ijhydene.2022.10.106>.
- [5] I. Syazaidah, M.S. Abu Bakar, M.S. Reza, A.K. Azad, Ex-situ catalytic pyrolysis of chicken litter for bio-oil production: Experiment and characterization, *J. Environ. Manage.* 297 (2021) 113407, <https://doi.org/10.1016/j.jenvman.2021.113407>.
- [6] O.E.da Silva Júnior, J.A.de Lima, R. Abrahão, M.H.A.de Lima, E.P. Santos Júnior, L.M. Coelho Junior, Solar heating with flat-plate collectors in residential buildings: A review, *Energies (Basel)* 15 (2022) 6130, <https://doi.org/10.3390/en15176130>.
- [7] Z. Liu, Q. Zhou, Z. Tian, B. He, G. Jin, A comprehensive analysis on definitions, development, and policies of nearly zero energy buildings in China, *Renew. Sustain. Energy Rev.* 114 (2019) 109314, <https://doi.org/10.1016/j.rser.2019.109314>.
- [8] A.P. Panunzi, L. Duranti, I. Luisetto, N. Lisi, M. Marelli, E. Di Bartolomeo, Triggering electrode multi-catalytic activity for reversible symmetric solid oxide cells by Pt-doping lanthanum strontium ferrite, *Chem. Eng. J.* 471 (2023) 144448, <https://doi.org/10.1016/j.cej.2023.144448>.
- [9] S.A. Muhammed Ali, M. Anwar, N. Ashikin, A. Muchtar, M.R. Somalu, Influence of oxygen ion enrichment on optical, mechanical, and electrical properties of LSCF perovskite nanocomposite, *Ceram. Int.* 44 (2018) 10433–10442, <https://doi.org/10.1016/j.ceramint.2018.03.060>.
- [10] S.A. Muhammed Ali, M. Anwar, M.R. Somalu, A. Muchtar, Enhancement of the interfacial polarization resistance of $\text{La}_{0.6}\text{Sr}_{0.4}\text{Co}_{0.2}\text{Fe}_{0.8}\text{O}_{3-\delta}$ cathode by microwave-assisted combustion method, *Ceram. Int.* 43 (2017) 4647–4654, <https://doi.org/10.1016/j.ceramint.2016.12.136>.
- [11] L.A. Omeiza, M. Abid, Y. Subramanian, A. Dhanasekaran, S.A. Bakar, A.K. Azad, Challenges, limitations, and applications of nanofluids in solar thermal collectors—A comprehensive review, *Environ. Sci. Pollut. Res.* (2023), <https://doi.org/10.1007/s11356-023-30656-9>.
- [12] L.A. Omeiza, M. Abid, Y. Subramanian, A. Dhanasekaran, M.d.M. Rahman, S. A. Bakar, et al., Limitations and challenges of heat transfer enhancement techniques in solar thermal collectors: A review, *J. Cent. South Univ.* 30 (2023) 3538–3574.
- [13] L.A. Omeiza, M. Abid, A. Dhanasekaran, Y. Subramanian, V. Raj, K. Kozak, et al., Application of Solar thermal collectors for energy consumption in public buildings—an updated technical review, *J. Eng. Res.* (2023), <https://doi.org/10.1016/j.jer.2023.09.011>.
- [14] M.A. Yatoo, S.J. Skinner, Ruddlesden-Popper phase materials for solid oxide fuel cell cathodes: A short review, *Mater. Today Proc.* 56 (2022) 3747–3754, <https://doi.org/10.1016/j.matpr.2021.12.537>.
- [15] W. Zhang, Y.H. Hu, Material design and performance of carbon monoxide-fueled solid oxide fuel cells: A review, *Energy Sci. Eng.* 11 (2023) 3276–3288, <https://doi.org/10.1002/ese3.1502>.
- [16] Q. Xu, Z. Guo, L. Xia, Q. He, Z. Li, I. Temitope Bello, et al., A comprehensive review of solid oxide fuel cells operating on various promising alternative fuels, *Energy Convers. Manage.* 253 (2022) 115175, <https://doi.org/10.1016/j.enconman.2021.115175>.
- [17] M. Fallah Vostakola, H.B. Amini, Progress in material development for low-temperature solid oxide fuel cells: A review, *Energies (Basel)* 14 (2021) 1280, <https://doi.org/10.3390/en14051280>.
- [18] S.Y. Istomin, N.V. Lyskov, G.N. Mazo, E.V. Antipov, Electrode materials based on complex d-metal oxides for symmetrical solid oxide fuel cells, *Russ. Chem. Rev.* 90 (2021) 644–676, <https://doi.org/10.1070/RCR4979>.
- [19] D. Udomsilp, C. Lenser, O. Guillon, N.H. Menzler, Performance benchmark of planar solid oxide cells based on material development and designs, *Energy Technol.* (2021) 9, <https://doi.org/10.1002/ente.202001062>.
- [20] M. Singh, D. Zappa, E. Comini, Solid oxide fuel cell: Decade of progress, future perspectives and challenges, *Int. J. Hydrogen Energy* 46 (2021) 27643–27674, <https://doi.org/10.1016/j.ijhydene.2021.06.020>.
- [21] M.Z. Ahmad, S.H. Ahmad, R.S. Chen, A.F. Ismail, R. Hazan, N.A. Baharuddin, Review on recent advancement in cathode material for lower and intermediate temperature solid oxide fuel cells application, *Int. J. Hydrogen Energy* 47 (2022) 1103–1120, <https://doi.org/10.1016/j.ijhydene.2021.10.094>.
- [22] C. Mendonça, A. Ferreira, D.M.F. Santos, Towards the commercialization of solid oxide fuel cells: Recent advances in materials and integration strategies, *Fuels* 2 (2021) 393–419, <https://doi.org/10.3390/fuels2040023>.
- [23] Y. Liu, Z. Shao, T. Mori, S.P. Jiang, Development of nickel based cermet anode materials in solid oxide fuel cells – Now and future, *Mater. Rep. Energy* 1 (2021) 100003, <https://doi.org/10.1016/j.matre.2020.11.002>.
- [24] I.T. Bello, S. Zhai, S. Zhao, Z. Li, N. Yu, M. Ni, Scientometric review of proton-conducting solid oxide fuel cells, *Int. J. Hydrogen Energy* 46 (2021) 37406–37428, <https://doi.org/10.1016/j.ijhydene.2021.09.061>.
- [25] M.A. Morales-Zapata, A. Larrea, M.A. Laguna-Bercero, Lanthanide nickelates for their application on solid oxide cells, *Electrochim. Acta* 444 (2023) 141970, <https://doi.org/10.1016/j.electacta.2023.141970>.

- [26] L.A. Omeiza, Md. Mosfiur Rahman, Y. Subramanian, U. Mamudu, J. Taweeekun, A.K. Azad, Synthesis, structure and characterization of $\text{Sr}_{0.9}\text{Y}_{0.1}\text{Ti}_{1-x}\text{V}_x\text{O}_3$ ($x = 0.1, 0.2$) anodes for solid oxide fuel cell, *J. Adv. Res. Micro Nano Eng.* 19 (2024) 107–114, <https://doi.org/10.37934/armne.19.1.107114>.
- [27] M. Choolaei, E. Jakubczyk, H.B. Amini, Synthesis and characterisation of a ceria-based cobalt-zinc anode nanocomposite for low-temperature solid oxide fuel cells (LT-SOFCs), *Electrochim. Acta* 445 (2023) 142057, <https://doi.org/10.1016/j.electacta.2023.142057>.
- [28] C. Xia, Z. Li, S. Wang, B.A. Beshiwork, B. Lin, Recent progress on efficient perovskite ceramic anodes for high-performing solid oxide fuel cells, *Int. J. Hydrogen Energy* 62 (2024) 331–344, <https://doi.org/10.1016/j.ijhydene.2024.02.364>.
- [29] X. Zhu, H. Yan, Q. Zhong, X. Zhao, W. Tan, $\text{Ce}_{0.9}\text{Sr}_{0.1}\text{Cr}_{0.5}\text{Mn}_{0.5}\text{O}_{3-\delta}$ as the anode materials for solid oxide fuel cells running on H_2 and H_2S , *Korean J. Chem. Eng.* 28 (2011) 1764–1769, <https://doi.org/10.1007/s11814-011-0033-5>.
- [30] J. Zamudio-García, J.M. Porras-Vázquez, E.R. Losilla, D. Marrero-López, LaCrO_3 - CeO_2 -based nanocomposite electrodes for efficient symmetrical solid oxide fuel cells, *ACS Appl. Energy Mater.* 5 (2022) 4536–4546, <https://doi.org/10.1021/acsaem.1c04116>.
- [31] J. Lach, K. Zheng, R. Kluczkowski, A. Niemczyk, H. Zhao, M. Chen, Tuning Cu-content $\text{La}_{1-x}\text{Sr}_x\text{Ni}_{1-y}\text{Cu}_y\text{O}_{3-\delta}$ with strontium doping as cobalt-free cathode materials for high-performance anode-supported IT-SOFCs, *Materials* 15 (2022) 8737, <https://doi.org/10.3390/ma15248737>.
- [32] J. Macías, J.R. Frade, A.A. Yaremchenko, SrTiO_3 - SrVO_3 ceramics for solid oxide fuel cell anodes: A route from oxidized precursors, *Materials* 16 (2023) 7638, <https://doi.org/10.3390/ma16247638>.
- [33] Y. Zhang, X. Zhang, J. Ni, C. Ni, Pr-Doped $\text{SrTi}_{0.5}\text{Mn}_{0.5}\text{O}_{3-\delta}$ as an electrode material for a quasi-symmetrical solid oxide fuel cell using methane and propane fuel, *ACS Appl. Mater. Interfaces* 15 (2023) 3974–3984, <https://doi.org/10.1021/acsaami.2c18530>.
- [34] Y. Gao, X. Huang, Z. Wang, M. Yuan, J. Gao, Z. Lv, et al., Cr deposition and poisoning on $\text{SrCo}_{0.9}\text{Ta}_{0.1}\text{O}_{3-\delta}$ cathode of solid oxide fuel cells, *Int. J. Hydrogen Energy* 48 (2023) 2341–2350, <https://doi.org/10.1016/j.ijhydene.2022.10.105>.
- [35] M.H. Ghozza, I.S. Yahia, M.S.A. Hussien, Structure, magnetic, and photocatalysis of $\text{La}_{0.7}\text{Sr}_{0.3}\text{MO}_3$ ($M = \text{Mn}, \text{Co}$, and Fe) perovskite nanoparticles: Novel photocatalytic materials, *Environ. Sci. Pollut. Res.* 30 (2023) 61106–61122, <https://doi.org/10.1007/s11356-023-26411-9>.
- [36] S.E. Wolf, F.E. Winterhalter, V. Vibhu, L.G.J. (Bert) de Haart, O. Guillon, R.-A. Eichel, et al., Solid oxide electrolysis cells – current material development and industrial application, *J. Mater. Chem. A Mater.* 11 (2023) 17977–18028, <https://doi.org/10.1039/D3TA02161K>.
- [37] J. Cheng, J. Gong, S. Yue, Y. Jiang, X. Hou, J. Ma, et al., Electrochemical investigation of $\text{La}_{0.4}\text{Sr}_{0.6}\text{TiO}_3$ synthesized in air for SOFC application, *J. Appl. Electrochem.* 51 (2021) 1175–1188, <https://doi.org/10.1007/s10800-021-01568-8>.
- [38] L.A. Omeiza, A.M. Abdalla, B. Wei, A. Dhanasekaran, Y. Subramanian, S. Afroze, et al., Nanostructured electrocatalysts for advanced applications in fuel cells, *Energies (Basel)* 16 (2023) 1876, <https://doi.org/10.3390/en16041876>.
- [39] L.A. Omeiza, K.A. Kuterbekov, A. Kabyshev, K. Bekmyrza, M. Kubenova, S. Afroze, et al., Limitations and trends on cobalt-free cathode materials development for intermediate-temperature solid oxide fuel cell: an updated technical review, *Emergent Mater.* (2024), <https://doi.org/10.1007/s42247-024-00737-7>.
- [40] J. Yang, H. Li, R. Zhou, C. Du, S. Wang, Preparation and properties of anode material LSCM for SOFC, *J. Alloy. Compd.* 986 (2024) 174145, <https://doi.org/10.1016/j.jallcom.2024.174145>.
- [41] L. Thommy, M. Benamira, T. Jardiell, V. Günes, O. Joubert, M.T. Caldes, Ru exsolution in substituted $\text{La}_{0.75}\text{Sr}_{0.25}\text{Cr}_{0.5}\text{Mn}_{0.5}\text{O}_{3-\delta}$ compound as anode material for an IT-SOFCs, *Mater. Chem. Phys.* 268 (2021) 124724, <https://doi.org/10.1016/j.matchemphys.2021.124724>.
- [42] E.G. Kalinina, D.S. Rusakova, K.S. Shubin, L.V. Ermakova, E.Y. Pikalova, CeO_2 -based thin-film electrolyte membranes for intermediate temperature SOFCs: Direct electrophoretic deposition on the supporting anode from additive-modified suspensions, *Int. J. Hydrogen Energy* (2023), <https://doi.org/10.1016/j.ijhydene.2023.01.159>.
- [43] M. Kiani, M.H. Paydar, $\text{SrCo}_{0.8}\text{Fe}_{0.1}\text{Ga}_{0.1}\text{O}_{3-\delta}$ (SCFG) cathodes incorporated with $\text{Sm}_{0.2}\text{Ce}_{0.8}\text{O}_{1.9}$ (SDC) for IT-SOFCs application, *J. Mater. Sci. Mater. Electron.* 34 (2023) 1366, <https://doi.org/10.1007/s10854-023-10773-4>.
- [44] J. Zan, S. Wang, D. Zheng, F. Li, W. Chen, Q. Pei, et al., Characterization and functional application of $\text{PrBa}_{0.5}\text{Sr}_{0.5}\text{Co}_{1.5}\text{Fe}_{0.5}\text{O}_{5+\delta}$ cathode material for IT-SOFC, *Mater. Res. Bull.* 137 (2021) 111173, <https://doi.org/10.1016/j.materresbull.2020.111173>.
- [45] X. Wang, R. Li, T. Hu, M. Wang, L. Zhang, C. Zhao, Mechanical behavior of YSZ-glass composite seals for solid oxide fuel cell application, *Ceram. Int.* 49 (2023) 995–1001, <https://doi.org/10.1016/j.ceramint.2022.09.074>.
- [46] J. Gao, Z. Liu, M. Akbar, C. Gao, W. Dong, Y. Meng, et al., Efficiently enhance the proton conductivity of YSZ-based electrolyte for low temperature solid oxide fuel cell, *Ceram. Int.* 49 (2023) 5637–5645, <https://doi.org/10.1016/j.ceramint.2022.10.181>.
- [47] H. Ding, Z. Tao, S. Liu, Y. Yang, A redox-stable direct-methane solid oxide fuel cell (SOFC) with $\text{Sr}_2\text{FeNb}_{0.2}\text{Mo}_{0.8}\text{O}_{6-\delta}$ double perovskite as anode material, *J. Power Sources* 327 (2016) 573–579, <https://doi.org/10.1016/j.jpowsour.2016.07.101>.
- [48] S. Choi, Electrochemical properties of Sr-doped layered perovskite as a promising anode material for direct hydrocarbon SOFCs, *J. Korean Ceram. Soc.* 57 (2020) 409–415, <https://doi.org/10.1007/s43207-020-00045-w>.
- [49] L. Fu, J. Zhou, J. Yang, Z. Lian, J. Wang, Y. Cheng, et al., Exsolution of Cu nanoparticles in $(\text{LaSr})_{0.9}\text{Fe}_{0.9}\text{Cu}_{0.1}\text{O}_4$ Ruddlesden-Popper oxide as symmetrical electrode for solid oxide cells, *Appl. Surf. Sci.* 511 (2020) 145525, <https://doi.org/10.1016/j.apsusc.2020.145525>.
- [50] B.J.M. Sarruf, J.-E. Hong, R. Steinberger-Wilckens, P.E.V. de Miranda, Influence of novel anode design on the performance and coke resistance towards methane directly-fed solid oxide fuel cells, *Ceram. Int.* 46 (2020) 5368–5379, <https://doi.org/10.1016/j.ceramint.2019.10.292>.
- [51] Y. Wan, Y. Xing, Y. Xie, N. Shi, J. Xu, C. Xia, Vanadium-doped strontium molybdate with exsolved Ni nanoparticles as anode material for solid oxide fuel cells, *ACS Appl. Mater. Interfaces* 11 (2019) 42271–42279, <https://doi.org/10.1021/acsaami.9b15584>.
- [52] N. Hou, P. Li, T. Lv, T. Yao, X. Yao, T. Gan, et al., $\text{Sm}_{0.5}\text{Ba}_{0.5}\text{MnO}_{3-\delta}$ anode for solid oxide fuel cells with hydrogen and methanol as fuels, *Catal. Today* 298 (2017) 33–39, <https://doi.org/10.1016/j.cattod.2017.06.034>.
- [53] S.S. Rathore, A.P. Kulkarni, D. Fini, S. Giddey, Evaluation of $(\text{La}_{0.6}\text{Sr}_{0.4})_{0.95}\text{Co}_{0.2}\text{Fe}_{0.8}\text{O}_{3-\delta}$ -Ag composite anode for direct ammonia solid oxide fuel cells and effect of Pd impregnation on the electrochemical performance, *Solids* 2 (2021) 177–191, <https://doi.org/10.3390/solids2020012>.
- [54] K. Hosoi, T. Sakai, S. Ida, T. Ishihara, Oxygen nonstoichiometry and cathodic property of $\text{Ce}_{0.6}\text{Mn}_{0.3}\text{Fe}_{0.1}\text{O}_{2-\delta}$ for high temperature steam electrolysis cell using LaGaO_3 -based oxide electrolyte, *ECS Meeting Abstracts* (2015) 313, <https://doi.org/10.1149/MA2015-03/1/313>.
- [55] A.C. Tomkiewicz, M.A. Tamimi, A. Huq, S. McIntosh, Structural analysis of $\text{PrBaMn}_2\text{O}_{5+\delta}$ under SOFC anode conditions by in-situ neutron powder diffraction, *J. Power Sources* 330 (2016) 240–245, <https://doi.org/10.1016/j.jpowsour.2016.09.013>.
- [56] W. Hao, Y. Mi, A direct carbon fuel cell with a CuO - ZnO -SDC composite anode, *RSC Adv.* 6 (2016) 50201–50208, <https://doi.org/10.1039/C6RA04949D>.
- [57] R. Pichandi, P. Tiwari, S. Basu, S. Singh, $\text{Ca}_2\text{Fe}_2\text{O}_5$ and $\text{Ca}_2\text{Co}_2\text{O}_5$ based composite cathode for IT-SOFC application, *Solid State Ion.* 404 (2024) 116418, <https://doi.org/10.1016/j.ssi.2023.116418>.
- [58] X. Bao, Z. Wang, Z. Song, X. Chen, X. Su, X. Han, et al., Effects of high-valence Mo content on microstructure and properties of $\text{Ba}_2\text{Fe}_2\text{O}_5$ - MoO_6 anode materials for solid oxide fuel cells, *J. Alloy. Compd.* 976 (2024) 173271, <https://doi.org/10.1016/j.jallcom.2023.173271>.
- [59] R. Packiaraj, A. Sreelakshmi, J. Ramya, S.S. Kumar, S.T. Aruna, Investigation on $\text{SmBa}_{0.5}\text{Sr}_{0.5}\text{Co}_{1.5}\text{Fe}_{0.5}\text{O}_{5+\delta}$ double perovskite as an oxygen electrode for reversible solid oxide fuel cell, *Mater. Today Commun.* 38 (2024) 108355, <https://doi.org/10.1016/j.mtcomm.2024.108355>.
- [60] H. Jeong, D. Kim, B. Sharma, J.H. Noh, K.T. Lee, J. Myung, Surface decorated $\text{La}_{0.45}\text{Ca}_{0.37}\text{Ni}_{0.06}\text{Ti}_{0.94}\text{O}_{3-\delta}$ as an anode functional layer for solid oxide fuel cell applications, *Korean J. Chem. Eng.* 37 (2020) 1440–1444, <https://doi.org/10.1007/s11814-020-0623-1>.
- [61] T. Chen, Y. Xie, Z. Lu, L. Wang, Z. Chen, X. Zhong, et al., $\text{La}_{0.75}\text{Sr}_{0.25}\text{Cr}_{0.5}\text{Mn}_{0.5}\text{O}_{3-\delta}$ - $\text{Ce}_{0.8}\text{Gd}_{0.2}\text{O}_{1.9}$ composite electrodes as anodes in LaGaO_3 -based direct carbon solid oxide fuel cells, *J. Cent. South Univ.* 29 (2022) 1788–1798, <https://doi.org/10.1007/s11771-022-5045-2>.
- [62] V. Cascos, M.T. Fernández-Díaz, J.A. Alonso, Al-doped SrMoO_3 perovskites as promising anode materials in solid oxide fuel cells, *Materials* 15 (2022) 3819, <https://doi.org/10.3390/ma15113819>.
- [63] Y. Dong, J. Li, Oxide cathodes: Functions, instabilities, self healing, and degradation mitigations, *Chem. Rev.* 123 (2023) 811–833, <https://doi.org/10.1021/acs.chemrev.2c00251>.
- [64] Q. Lyu, T. Zhu, Z. Li, K. Sun, C. Jin, M. Han, et al., Enhancement of the cathode/electrolyte interface by a sintering-active barrier layer for solid oxide fuel cells, *Int. J. Hydrogen Energy* 48 (2023) 15238–15247, <https://doi.org/10.1016/j.ijhydene.2023.01.028>.
- [65] S. Im, J.-H. Lee, H.-I. Ji, $\text{PrBa}_{0.5}\text{Sr}_{0.5}\text{Co}_{1.5}\text{Fe}_{0.5}\text{O}_{5+\delta}$ composite cathode in protonic ceramic fuel cells, *J. Korean Ceram. Soc.* 58 (2021) 351–358, <https://doi.org/10.1007/s43207-021-00109-5>.
- [66] H. Bai, J. Chu, T. Chen, Z. Leng, B. Zhang, Y. Zhang, et al., $\text{PrBa}_{0.5}\text{Sr}_{0.5}\text{Co}_{1.5}\text{Fe}_{0.5}\text{O}_{5+\delta}$ as air electrode for proton-conducting solid oxide cells, *J. Power Sources* 574 (2023) 233162, <https://doi.org/10.1016/j.jpowsour.2023.233162>.
- [67] Y. Lim, J. Park, H. Lee, M. Ku, Y.-B. Kim, Rapid fabrication of lanthanum strontium cobalt ferrite (LSCF) with suppression of LSCF/YSZ chemical side reaction via flash light sintering for SOFCs, *Nano Energy* 90 (2021) 106524, <https://doi.org/10.1016/j.nanoen.2021.106524>.
- [68] C. Timurkutluk, F. Yildirim, F. Toruntay, S. Onbilgin, M. Yagiz, B. Timurkutluk, Fabrication and optimization of LSM infiltrated cathode electrode for anode supported microtubular solid oxide fuel cells, *Int. J. Hydrogen Energy* 48 (2023) 9833–9844, <https://doi.org/10.1016/j.ijhydene.2022.12.141>.
- [69] J.H. Kim, D. Kim, S. Ahn, K.J. Kim, S. Jeon, D.-K. Lim, et al., An universal oxygen electrode for reversible solid oxide electrochemical cells at reduced temperatures, *Energy Environ. Sci.* 16 (2023) 3803–3814, <https://doi.org/10.1039/D2EE04108A>.
- [70] K. Develos-Bagarinao, T. Ishiyama, H. Kishimoto, H. Shimada, K. Yamaji, Nanoengineering of cathode layers for solid oxide fuel cells to achieve superior power densities, *Nat. Commun.* 12 (2021) 3979, <https://doi.org/10.1038/s41467-021-24255-w>.
- [71] X.-D. Zhou, S.C. Singhal, FUEL CELLS – SOLID OXIDE FUEL CELLS | Overview. Encyclopedia of Electrochemical Power Sources, Elsevier; 2009, p. 1–16. doi: 10.1016/B978-0-444-52745-5.00250-1.
- [72] G. Dash, E. Rout, Investigation of structural, electrical and electrochemical properties of $\text{La}_{0.8}\text{Sr}_{0.2}\text{Mn}_{1-x}\text{Sc}_x\text{O}_{3-\delta}$ as cathode on yttria-stabilized zirconia

- electrolyte for intermediate temperature solid oxide fuel cell fabricated by one step dry pressing method, *J. Mater. Sci. Mater. Electron.* 35 (2024) 491, <https://doi.org/10.1007/s10854-024-12224-0>.
- [73] Z. Li, T. Wu, Z. Zhang, H. Sun, X. Guo, Q. Hu, et al., Experimental study and first-principles calculation of enhanced electrochemical properties of $\text{Bi}_{0.7}\text{Sr}_{0.3}\text{FeO}_{3-\delta}$ (BSFO) – $\text{La}_{0.8}\text{Sr}_{0.2}\text{MnO}_{3-\delta}$ (LSM) composite cathodes for intermediate-temperature solid oxide fuel cells, *J. Power Sources* 591 (2024) 233898, <https://doi.org/10.1016/j.jpowsour.2023.233898>.
- [74] W. Jia, Y. Wang, J. Huang, M. Li, B. Xiang, Y. Wang, et al., Alternative B-site-doped $\text{La}_{0.6}\text{Sr}_{0.4}\text{Co}_{0.2}\text{Fe}_{0.8-x}\text{M}_x\text{O}_3$ ($\text{M} = \text{Ni, Cu, Nb; } x = 0, 0.1, 0.2$) as innovative cathode material for LT-SOFC with enhanced charge transfer and oxygen ion diffusion, *Appl. Energy* 353 (2024) 122096, <https://doi.org/10.1016/j.apenergy.2023.122096>.
- [75] N. Shah, X. Xu, J. Love, H. Wang, Z. Zhu, L. Ge, Mitigating thermal expansion effects in solid oxide fuel cell cathodes: A critical review, *J. Power Sources* 599 (2024) 234211, <https://doi.org/10.1016/j.jpowsour.2024.234211>.
- [76] L. Hu, D. Zhou, X. Zhu, N. Wang, J. Bai, H. Gong, et al., A high-performance composite cathode based on thermal expansion complementation for SOFC, *Fuel* 362 (2024) 130864, <https://doi.org/10.1016/j.fuel.2024.130864>.
- [77] D. Zhang, K. Liao, Y. Yu, Z. Tian, Y. Cao, Microstructure and thermal & mechanical properties of $\text{La}_2\text{Zr}_2\text{O}_7/\text{YSZ}$ composite ceramic, *Ceram. Int.* 46 (2020) 4737–4747, <https://doi.org/10.1016/j.ceramint.2019.10.205>.
- [78] S. Manishanna, A. Dutta, Synthesis and characterization of nickel doped LSM as possible cathode materials for LT-SOFC application, *Mater. Chem. Phys.* 297 (2023) 127438, <https://doi.org/10.1016/j.matchemphys.2023.127438>.
- [79] A.Y. Zuev, A.N. Petrov, A.I. Vylkov, D.S. Tsvetkov, Oxygen nonstoichiometry and defect structure of undoped and doped lanthanum cobaltites, *J. Mater. Sci.* 42 (2007) 1901–1908, <https://doi.org/10.1007/s10853-006-0345-8>.
- [80] M. Kumar, S. Srikanth, B. Ravikumar, T.C. Alex, S.K. Das, Synthesis of pure and Sr-doped LaGaO_3 , LaFeO_3 and LaCoO_3 and Sr, Mg-doped LaGaO_3 for ITSOFC application using different wet chemical routes, *Mater. Chem. Phys.* 113 (2009) 803–815, <https://doi.org/10.1016/j.matchemphys.2008.08.047>.
- [81] D. Berger, C. Matei, F. Papa, G. Voicu, V. Fruth, Pure and doped lanthanum cobaltites obtained by combustion method, *Prog. Solid State Chem.* 35 (2007) 183–191, <https://doi.org/10.1016/j.progsolidstchem.2007.01.001>.
- [82] M.M. Natile, G. Eger, P. Batocchi, F. Mauvy, A. Glisenti, Strontium and copper doped LaCoO_3 : New cathode materials for solid oxide fuel cells? *Int. J. Hydrogen Energy* 42 (2017) 1724–1735, <https://doi.org/10.1016/j.ijhydene.2016.09.127>.
- [83] M. Karimi-Nazarabad, H. Ahmadvadeh, E.K. Goharshadi, Porous perovskite-lanthanum cobaltite as an efficient cocatalyst in photoelectrocatalytic water oxidation by bismuth doped $\text{g-C}_3\text{N}_4$, *Sol. Energy* 227 (2021) 426–437, <https://doi.org/10.1016/j.solener.2021.09.028>.
- [84] D.A. Kumar, S. Selvasekarapandian, H. Nithya, J. Leiro, Y. Masuda, S.-D. Kim, et al., Effect of calcium doping on LaCoO_3 prepared by Pechini method, *Powder Technol.* 235 (2013) 140–147, <https://doi.org/10.1016/j.powtec.2012.09.030>.
- [85] H.J. Hwang, J. Moon, M. Awano, K. Maeda, Sol-gel route to porous lanthanum cobaltite (LaCoO_3) thin films, *J. Am. Ceram. Soc.* 83 (2004) 2852–2854, <https://doi.org/10.1111/j.1151-2916.2000.tb01643.x>.
- [86] L.A. Omeiza, U. Mamudu, Y. Subramanian, A. Dhanasekaran, M.M. Rahman, S. A. Bakar, et al., Structure and electrochemical characterization of $\text{Nd}_{0.5}\text{Ba}_{0.5}\text{Zr}_{0.8}\text{Fe}_{0.2}\text{O}_{3-\delta}$ cobalt-free cathode material for intermediate-temperature solid oxide fuel cells: An experimental investigation, *Johnson Matthey Technol. Rev.* (2024), <https://doi.org/10.1595/205651324X17048121572464>.
- [87] K.H. Tan, H.A. Rahman, M.S. Azami, U.A. Yusop, N.A. Baharuddin, M.I. N. Ma'arof, Electrochemical and material characteristics of $\text{Ba}_{0.5}\text{Sr}_{0.5}\text{Co}_{0.8}\text{Fe}_{0.2}\text{O}_{3-\delta}\text{Sm}_{0.2}\text{Ce}_{0.8}\text{O}_{1.9}$ carbonate perovskite cathode composite for low-temperature solid oxide fuel cell, *Ceram. Int.* 48 (2022) 34258–34264, <https://doi.org/10.1016/j.ceramint.2022.07.325>.
- [88] N. Li, L. Sun, Q. Li, T. Xia, L. Huo, H. Zhao, Electrode properties of CuBi_2O_4 spinel oxide as a new and potential cathode material for solid oxide fuel cells, *J. Power Sources* 511 (2021) 230447, <https://doi.org/10.1016/j.jpowsour.2021.230447>.
- [89] H.-X. Zhang, J.-X. Yang, P.-F. Wang, C.-G. Yao, X.-D. Yu, F.-N. Shi, Novel cobalt-free perovskite $\text{PrBaFe}_{1.9}\text{Mo}_{0.1}\text{O}_{5+}$ as a cathode material for solid oxide fuel cells, *Solid State Ion.* 391 (2023) 116144, <https://doi.org/10.1016/j.ssi.2023.116144>.
- [90] A.I. Klyndyuk, D.S. Kharytonau, M. Mosialek, E.A. Chizhova, A. Komenda, R. P. Socha, et al., Double substituted $\text{NdBa}(\text{Fe, Co, Cu})\text{ZrO}_{5+\delta}$ layered perovskites as cathode materials for intermediate-temperature solid oxide fuel cells – correlation between structure and electrochemical properties, *Electrochim. Acta* 411 (2022) 140062, <https://doi.org/10.1016/j.electacta.2022.140062>.
- [91] L. Zhang, S. Yu, Y. Gu, L. Bi, New $\text{BaZr}_{0.125}\text{Y}_{0.125}\text{M}_{0.75}\text{O}_3$ ($\text{M} = \text{Cu, Mn, Ni, Zn Co, and Fe}$) cathodes for proton-conducting solid oxide fuel cells, *Int. J. Hydrogen Energy* 71 (2024) 1214–1221, <https://doi.org/10.1016/j.ijhydene.2024.05.271>.
- [92] C. Liu, B. Ma, Z. Lin, Y. Zhou, K. Wu, Exploring $(1-x)\text{CuFe}_2\text{O}_4\text{-xGd}_{0.4}\text{Ce}_{0.9}\text{O}_{1.95}$ composites as the cathode materials for solid oxide fuel cells, *Mater. Lett.* 325 (2022) 132860, <https://doi.org/10.1016/j.matlet.2022.132860>.
- [93] W. Xia, X. Liu, F. Jin, X. Jia, Y. Shen, J. Li, Evaluation of calcium codoping in double perovskite $\text{PrBaCo}_2\text{O}_{5+}$ as cathode material for IT-SOFCs, *Electrochim. Acta* 364 (2020) 137274, <https://doi.org/10.1016/j.electacta.2020.137274>.
- [94] X. Li, C. Shi, G. Zhang, G. Zheng, Z. Huang, X. Shen, et al., A medium-entropy perovskite oxide $\text{La}_{0.7}\text{Sr}_{0.3}\text{Co}_{0.25}\text{Fe}_{0.25}\text{Ni}_{0.25}\text{Mn}_{0.25}\text{O}_{3-\delta}$ as intermediate temperature solid oxide fuel cells cathode material, *Ceram. Int.* 49 (2023) 30187–30195, <https://doi.org/10.1016/j.ceramint.2023.06.275>.
- [95] H. Zhang, K. Xu, Y. Xu, F. He, F. Zhu, L. Zhu, et al., Improving the performance of the $\text{PrBa}_{0.8}\text{Ca}_{0.2}\text{Co}_2\text{O}_{5+\delta}$ cathode for proton-conducting SOFCs by microwave sintering, *Ceram. Int.* (2024), <https://doi.org/10.1016/j.ceramint.2024.05.299>.
- [96] D. Li, X. Zhang, C. Liang, Y. Jin, M. Fu, J. Yuan, et al., Study on durability of novel core-shell-structured $\text{La}_{0.8}\text{Sr}_{0.2}\text{Co}_{0.2}\text{Fe}_{0.8}\text{O}_{3-\delta}/\text{Gd}_{0.2}\text{Ce}_{0.8}\text{O}_{1.9}$ composite materials for solid oxide fuel cell cathodes, *Int. J. Hydrogen Energy* 46 (2021) 28221–28231, <https://doi.org/10.1016/j.ijhydene.2021.06.031>.
- [97] L. Zhang, Y. Yin, Y. Xu, S. Yu, L. Bi, Tailoring $\text{Sr}_2\text{Fe}_{1.5}\text{Mo}_{0.5}\text{O}_{6-\delta}$ with Sc as a new single-phase cathode for proton-conducting solid oxide fuel cells, *Sci. China Mater.* 65 (2022) 1485–1494, <https://doi.org/10.1007/s40843-021-1935-5>.
- [98] S. Ahmed, W.W. Kazmi, A. Hussain, M.Z. Khan, S. Bibi, M. Saleem, et al., Facile and low-temperature synthesis approach to fabricate $\text{Sm}_{0.5}\text{Sr}_{0.5}\text{CoO}_{3-\delta}$ cathode material for solid oxide fuel cell, *J. Korean Ceram. Soc.* 60 (2023) 272–282, <https://doi.org/10.1007/s43207-022-00261-6>.
- [99] Y. Ma, L. Zhang, K. Zhu, B. Zhang, R. Peng, C. Xia, et al., In^{3+} -doped $\text{Sr}_2\text{Fe}_{1.5}\text{Mo}_{0.5}\text{O}_{6-\delta}$ cathode with improved performance for an intermediate-temperature solid oxide fuel cell, *Nano Res.* 17 (2024) 407–415, <https://doi.org/10.1007/s12274-023-6338-y>.
- [100] Q. Zeng, X. Zhang, W. Wang, D. Zhang, Y. Jiang, X. Zhou, et al., A Zn-doped $\text{Ba}_{0.5}\text{Sr}_{0.5}\text{Co}_{0.8}\text{Fe}_{0.2}\text{O}_{3-\delta}$ perovskite cathode with enhanced ORR catalytic activity for SOFCs, *Catalysts* 10 (2020) 235, <https://doi.org/10.3390/catal10020235>.
- [101] Y. Chen, T. Yu, J. Jin, H. Zhang, Triple perovskite $\text{Nd}_{1.5}\text{Ba}_{1.5}\text{CoFeMnO}_{9-\delta}\text{-Sm}_{0.2}\text{Ce}_{0.8}\text{O}_{1.9}$ composite as cathodes for the intermediate temperature solid oxide fuel cells, *Materials* 15 (2022) 3663, <https://doi.org/10.3390/ma15103663>.
- [102] N. Shaheen, Z. Chen, Y. Nong, T. Su, M. Yousaf, Y. Lu, et al., Enhancing ORR catalytic activity and electrochemical investigation of $\text{La}_{1-2x}\text{Ba}_x\text{Bi}_x\text{FeO}_3$ cathode for low-temperature solid oxide fuel cell, *Crystals (Basel)* 13 (2023) 822, <https://doi.org/10.3390/cryst13050822>.
- [103] M. Liang, F. He, C. Zhou, Y. Chen, R. Ran, G. Yang, et al., Nickel-doped $\text{BaCo}_{0.4}\text{Fe}_{0.4}\text{Zr}_{0.1}\text{Y}_{0.1}\text{O}_{3-\delta}$ as a new high-performance cathode for both oxygen-ion and proton conducting fuel cells, *Chem. Eng. J.* 420 (2021) 127717, <https://doi.org/10.1016/j.cej.2020.127717>.
- [104] X. Meng, X. Liu, D. Han, H. Wu, J. Li, Z. Zhan, Symmetrical solid oxide fuel cells with impregnated $\text{SrFe}_{0.75}\text{Mo}_{0.25}\text{O}_{3-\delta}$ electrodes, *J. Power Sources* 252 (2014) 58–63, <https://doi.org/10.1016/j.jpowsour.2013.11.049>.
- [105] Z. Gao, X. Ding, D. Ding, L. Ding, S. Zhang, G. Yuan, Infiltrated Pr_2NiO_4 as promising bi-electrode for symmetrical solid oxide fuel cells, *Int. J. Hydrogen Energy* 43 (2018) 8953–8961, <https://doi.org/10.1016/j.ijhydene.2018.03.164>.
- [106] X. Li, R. Li, Y. Tian, Y. Gao, S. Zhu, F. Jin, et al., Tuning $\text{Pr}_{0.5}\text{Ba}_{0.5}\text{FeO}_{3-\delta}$ cathode to enhanced stability and activity via Ca-doping for symmetrical solid oxide fuel cells, *Int. J. Hydrogen Energy* 60 (2024) 650–656, <https://doi.org/10.1016/j.ijhydene.2024.02.218>.
- [107] X. Zhang, S. Lin, Q. Zhou, $\text{Sr}_2\text{FeNi}_{0.2}\text{Cu}_{0.2}\text{Co}_{1.0}\text{Mo}_{0.5}\text{O}_6$ as potential symmetrical electrode for intermediate-temperature solid-oxide fuel cells, *Mater. Res. Bull.* 174 (2024) 112715, <https://doi.org/10.1016/j.materresbull.2024.112715>.
- [108] H.J. Lee, S.J. Son, S.K. Kim, S. Choi, M.K. Kim, T.H. Shin, et al., A-site and B-site co-doped $\text{PrBaFe}_{2.0}\text{O}_{5+\delta}$ double perovskite as a symmetrical electrode of solid oxide fuel cell with potential of CO_2 electrolysis, *J. Power Sources* 595 (2024) 234032, <https://doi.org/10.1016/j.jpowsour.2023.234032>.
- [109] C. Yang, Y. Wang, Y. Tian, Z. Wang, J. Pu, F. Ciucci, et al., Electrochemical performance of symmetric solid oxide cells employing a Sc-doped $\text{SrFeO}_{3-\delta}$ -based electrode, *Chem. Eng. J.* 485 (2024) 149970, <https://doi.org/10.1016/j.cej.2024.149970>.
- [110] F. He, X. Zhou, L. Liu, Y. Sheng, X. Jiang, Y. Tang, et al., High-performance low-temperature solid oxide fuel cell with a $\text{Pt@C-Ni}_{0.8}\text{Co}_{0.15}\text{Al}_{0.05}\text{LiO}_{2-\delta}$ composite cathode, *Energy Fuel* (2024), <https://doi.org/10.1021/acs.energyfuels.4c00629>.
- [111] N. Xu, S. Zhang, S. Su, J. Meng, L. Zhao, Z. Xu, Cobalt-free perovskite $\text{La}_{0.6}\text{Ba}_{0.4}\text{Ni}_{0.2}\text{Fe}_{0.8-x}\text{Ti}_{0.3}\text{O}_{3-\delta}$ ($x=0-0.3$) as cathode for intermediate-temperature solid oxide fuel cells, *Int. J. Hydrogen Energy* 50 (2024) 1064–1074, <https://doi.org/10.1016/j.ijhydene.2023.10.028>.
- [112] M. Chen, H. Zhang, C. Yao, H. Lou, Z. Zhang, B. Xia, et al., Ce-doping enhanced ORR kinetics and CO_2 tolerance of $\text{Nd}_{1-x}\text{Ce}_x\text{BaCoFeO}_{5+}$ ($x=0-0.2$) cathodes for solid oxide fuel cells, *Ceram. Int.* (2024), <https://doi.org/10.1016/j.ceramint.2024.02.325>.
- [113] K. Li, T. Tan, C. Yang, Z. Liao, J. Yang, *In Situ* exsolved CoFe alloy nanoparticles on $\text{Gd}_2\text{SrCo}_{0.8}\text{Fe}_{1.2}\text{O}_{7-\delta}$ for direct hydrocarbon fuel solid oxide fuel cells, *Energy Fuel* (2024), <https://doi.org/10.1021/acs.energyfuels.4c00538>.
- [114] M.B. Farias, A.J.M. Araújo, L.I.V. Holz, S.M. Mikhalev, C.A. Paskocimas, D. P. Fagg, et al., $\text{Sr}_2\text{Fe}_{1.5}\text{Mo}_{0.5}\text{O}_{6-\delta}$ -based cathodes for solid oxide fuel cells: Microstructural considerations and composite formation with Pr-doped ceria, *Int. J. Hydrogen Energy* 61 (2024) 1305–1316, <https://doi.org/10.1016/j.ijhydene.2024.02.363>.
- [115] W.H. Kan, A.J. Samson, V. Thangadurai, Trends in electrode development for next generation solid oxide fuel cells, *J. Mater. Chem. A Mater.* 4 (2016) 17913–17932, <https://doi.org/10.1039/C6TA06757C>.
- [116] A.P. Tarutin, E.A. Filonova, S. Ricote, D.A. Medvedev, Z. Shao, Chemical design of oxygen electrodes for solid oxide electrochemical cells: A guide, *Sustainable Energy Technol. Assess.* 57 (2023) 103185, <https://doi.org/10.1016/j.seta.2023.103185>.
- [117] N. Supanchaiyamat, A.J. Hunt, Conservation of critical elements of the periodic table, *ChemSusChem* 12 (2019) 397–403, <https://doi.org/10.1002/cssc.201802556>.
- [118] J.A. Jenkins, M. Musgrove, S.J.O. White, Outlining potential biomarkers of exposure and effect to critical minerals: Nutritionally essential trace elements and

- the rare earth elements, *Toxics* 11 (2023) 188, <https://doi.org/10.3390/toxics11020188>.
- [119] L.A. Omeiza, M.M. Rahman, K.A. Kuterbekov, A. Kabyshev, K. Bekmyrza, M. Kubenova, et al., Novel Sr-doped $\text{NdMn}_{0.5}\text{Cr}_{0.5}\text{O}_{3-\delta}$ electrodes for symmetrical solid oxide fuel cell, *Electrochem. Commun.* 164 (2024) 107730, <https://doi.org/10.1016/j.elecom.2024.107730>.
- [120] M.M. Rahman, A.M. Abdalla, L.A. Omeiza, V. Raj, S. Afroze, M.S. Reza, et al., Numerical modeling of ammonia-fueled protonic-ion conducting electrolyte-supported solid oxide fuel cell (H-SOFC): A brief review, *Processes* 11 (2023) 2728, <https://doi.org/10.3390/pr11092728>.